



NEW WORK ITEM PROPOSAL	
Date of presentation 2009-06-18	Reference number (to be given by the Secretariat)
Proposer DIN	ISO/TC 61 / SC 11
Secretariat JISC	N 938

A proposal for a new work item within the scope of an existing committee shall be submitted to the secretariat of that committee with a copy to the Central Secretariat and, in the case of a subcommittee, a copy to the secretariat of the parent technical committee. Proposals not within the scope of an existing committee shall be submitted to the secretariat of the ISO Technical Management Board.

The proposer of a new work item may be a member body of ISO, the secretariat itself, another technical committee or subcommittee, or organization in liaison, the Technical Management Board or one of the advisory groups, or the Secretary-General.

The proposal will be circulated to the P-members of the technical committee or subcommittee for voting, and to the O-members for information.

See overleaf for guidance on when to use this form.

IMPORTANT NOTE: Proposals without adequate justification risk rejection or referral to originator.

Guidelines for proposing and justifying a new work item are given overleaf.

Proposal (to be completed by the proposer)

Title of proposal (in the case of an amendment, revision or a new part of an existing document, show the reference number and current title)	
English title	Plastics — Extruded sheets of impact-modified acrylonitrile/styrene copolymers (ABS, AEPDS and ASA) — Requirements and test methods
French title (if available)	Plastiques — Plaques extrudées en copolymères d'acrylonitrile-styrène modifiés choc (ABS, AEPDS et ASA) — Exigences et méthodes d'essai
Scope of proposed project	
Correction of specified Charpy impact strength in ISO 15015:2007	
Concerns known patented items (see ISO/IEC Directives Part 1 for important guidance)	
<input type="checkbox"/> Yes <input checked="" type="checkbox"/> No If "Yes", provide full information as annex	
Envisaged publication type (indicate one of the following, if possible)	
<input checked="" type="checkbox"/> International Standard <input type="checkbox"/> Technical Specification <input type="checkbox"/> Publicly Available Specification <input type="checkbox"/> Technical Report	
Purpose and justification (attach a separate page as annex, if necessary)	
<p>The given values for the Charpy impact strength of notched specimen in ISO 15015:2007, Table 2 and Table 3, are valid for +23 degrees Celsius. Unfortunately, in the published version the temperature is specified as -20 degrees Celsius, which is incorrect. The present status of ISO 15015 resulted from a misunderstanding caused by the German Vote during the DIS stage in 2006. Our intention was to add additional values for minus 20 degrees (and not to change the specified temperature).</p> <p>To our knowledge, up to now assured values for the Charpy impact strength of notched specimen at -20 degrees are not available. Therefore, we propose to delete the specification for -20 degrees completely.</p> <p>Technically the given temperature has to be changed from -20 to +23 degrees Celsius.</p> <p>We propose to carry out this change on the fastest track possible since this mistake may lead to an incorrect execution of the standard ISO 15015.</p>	
Target date for availability (date by which publication is considered to be necessary)	
Proposed development track <input checked="" type="checkbox"/> 1 (24 months) <input type="checkbox"/> 2 (36 months - default) <input type="checkbox"/> 3 (48 months)	
Relevant documents to be considered	
ISO 15015:2007	
Relationship of project to activities of other international bodies	
—	
Liaison organizations	Need for coordination with:
—	<input type="checkbox"/> IEC <input type="checkbox"/> CEN <input type="checkbox"/> Other (please specify)

New work item proposal

<p>Preparatory work (at a minimum an outline should be included with the proposal)</p> <p><input checked="" type="checkbox"/> A draft is attached <input type="checkbox"/> An outline is attached. It is possible to supply a draft by</p> <p>The proposer or the proposer's organization is prepared to undertake the preparatory work required <input type="checkbox"/> Yes <input type="checkbox"/> No</p>	
<p>Proposed Project Leader (name and address)</p> <p>Dipl.-Ing. Benno Krott R&D Senior Engineer Quality Assurance Manager VitasheetGroup Metzeler Im Reinfeld 2 52428 Juelich-Kirchberg Germany E-Mail: benno.krott@vitasheetgroup.de</p>	<p>Name and signature of the Proposer (include contact information)</p> <p>Dr.-Ing. Arne Genz Plastics Committee Deutsches Institut fuer Normung e. V. 10772 Berlin Germany Tel. +49 30 2601-2451 E-Mail: arne.genz@din.de</p>
<p>Comments of the TC or SC Secretariat</p> <p>Supplementary information relating to the proposal</p> <p><input type="checkbox"/> This proposal relates to a new ISO document;</p> <p><input checked="" type="checkbox"/> This proposal relates to the amendment/revision of an existing ISO document;</p> <p><input type="checkbox"/> This proposal relates to the adoption as an active project of an item currently registered as a Preliminary Work Item;</p> <p><input type="checkbox"/> This proposal relates to the re-establishment of a cancelled project as an active project.</p> <p>Other:</p> <p>Voting information</p> <p>The ballot associated with this proposal comprises a vote on:</p> <p><input type="checkbox"/> Adoption of the proposal as a new project</p> <p><input type="checkbox"/> Adoption of the associated draft as a committee draft (CD)</p> <p><input checked="" type="checkbox"/> Adoption of the associated draft for submission for the enquiry vote (DIS or equivalent)</p> <p>Other: Due to the minor change we would propose to start with the highest possible stage.</p>	

Annex(es) are included with this proposal (give details)

Date of circulation	Closing date for voting	Signature of the TC or SC Secretary
2009-06-19		MURASHIGE, Masayuki/ JISC murashige@jpif.gr.jp

Use this form to propose:

- a) a new ISO document (including a new part to an existing document), or the amendment/revision of an existing ISO document;
- b) the establishment as an active project of a preliminary work item, or the re-establishment of a cancelled project;
- c) the change in the type of an existing document, e.g. conversion of a Technical Specification into an International Standard.

This form is not intended for use to propose an action following a systematic review - use ISO Form 21 for that purpose.

Proposals for correction (i.e. proposals for a Technical Corrigendum) should be submitted in writing directly to the secretariat concerned.

Guidelines on the completion of a proposal for a new work item

(see also the ISO/IEC Directives Part 1)

- a) **Title:** Indicate the subject of the proposed new work item.
- b) **Scope:** Give a clear indication of the coverage of the proposed new work item. Indicate, for example, if this is a proposal for a new document, or a proposed change (amendment/revision). It is often helpful to indicate what is not covered (exclusions).
- c) **Envisaged publication type:** Details of the types of ISO deliverable available are given in the ISO/IEC Directives, Part 1 and/or the associated ISO Supplement.
- d) **Purpose and justification:** Give details based on a critical study of the following elements wherever practicable. *Wherever possible reference should be made to information contained in the related TC Business Plan.*
 - 1) The specific aims and reason for the standardization activity, with particular emphasis on the aspects of standardization to be covered, the problems it is expected to solve or the difficulties it is intended to overcome.
 - 2) The main interests that might benefit from or be affected by the activity, such as industry, consumers, trade, governments, distributors.
 - 3) Feasibility of the activity: Are there factors that could hinder the successful establishment or global application of the standard?
 - 4) Timeliness of the standard to be produced: Is the technology reasonably stabilized? If not, how much time is likely to be available before advances in technology may render the proposed standard outdated? Is the proposed standard required as a basis for the future development of the technology in question?

New work item proposal

5) Urgency of the activity, considering the needs of other fields or organizations. Indicate target date and, when a series of standards is proposed, suggest priorities.

6) The benefits to be gained by the implementation of the proposed standard; alternatively, the loss or disadvantage(s) if no standard is established within a reasonable time. Data such as product volume or value of trade should be included and quantified.

7) If the standardization activity is, or is likely to be, the subject of regulations or to require the harmonization of existing regulations, this should be indicated.

If a series of new work items is proposed having a common purpose and justification, a common proposal may be drafted including all elements to be clarified and enumerating the titles and scopes of each individual item.

e) Relevant documents and their effects on global relevancy: List any known relevant documents (such as standards and regulations), regardless of their source. When the proposer considers that an existing well-established document may be acceptable as a standard (with or without amendment), indicate this with appropriate justification and attach a copy to the proposal.

f) Cooperation and liaison: List relevant organizations or bodies with which cooperation and liaison should exist.

ISO TC 61/SC 11 N938

Date: 2009-06-18

ISO/WD 15015

ISO TC 61/SC 11/WG 3

Secretariat: JISC

Plastics — Extruded sheets of impactmodified acrylonitrile-styrene copolymers (ABS, AEPDS and ASA) — Requirements and test methods

Plastiques — Plaques extrudées en copolymères d'acrylonitrile-styrène modifiés choc (ABS, AEPDS ou ASA) — Exigences et méthodes d'essai

Warning

This document is not an ISO International Standard. It is distributed for review and comment. It is subject to change without notice and may not be referred to as an International Standard.

Recipients of this draft are invited to submit, with their comments, notification of any relevant patent rights of which they are aware and to provide supporting documentation.

Copyright notice

This ISO document is a working draft or committee draft and is copyright-protected by ISO. While the reproduction of working drafts or committee drafts in any form for use by participants in the ISO standards development process is permitted without prior permission from ISO, neither this document nor any extract from it may be reproduced, stored or transmitted in any form for any other purpose without prior written permission from ISO.

Requests for permission to reproduce this document for the purpose of selling it should be addressed as shown below or to ISO's member body in the country of the requester:

[Indicate the full address, telephone number, fax number, telex number, and electronic mail address, as appropriate, of the Copyright Manger of the ISO member body responsible for the secretariat of the TC or SC within the framework of which the working document has been prepared.]

Reproduction for sales purposes may be subject to royalty payments or a licensing agreement.

Violators may be prosecuted.

Contents

Page

Foreword	iv
1 Scope	1
2 Normative references	1
3 Material	2
4 Requirements	2
4.1 Appearance	2
4.2 Dimensional tolerances	2
4.3 Properties	3
5 Test methods	4
5.1 Test specimens	4
5.2 Delivery condition	5
5.3 Appearance	5
5.4 Dimensions	5
5.5 Density	6
5.6 Mechanical properties	6
5.7 Thermal properties	6
6 Designation	9
7 Marking	10
Annex A (informativ) Additional guide values	11
Bibliography	12

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 15015 was prepared by Technical Committee ISO/TC 61, *Plastics*, Subcommittee SC 11, *Products*.

This second edition cancels and replaces the first edition (ISO 15015:2007), Table 2 and Table 3 of which have been revised.

Plastics — Extruded sheets of impactmodified acrylonitrile-styrene copolymers (ABS, AEPDS and ASA) — Requirements and test methods

1 Scope

This International Standard specifies the requirements and test methods for solid flat extruded sheets of impact-modified acrylonitrile-styrene copolymer materials: acrylonitrile-butadiene-styrene (ABS), acrylonitrile-(ethylene-propylene-diene)-styrene (AEPDS) (commonly known as AES) and acrylonitrile-styrene-acrylate (ASA), without fillers or reinforcing materials. This International Standard also applies to ABS, AEPDS and ASA sheet in rolled form. It applies only to thicknesses from 0,25 mm to 20,0 mm.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 179-1, *Plastics — Determination of Charpy impact properties — Part 1: Non-instrumented impact test*

ISO 179-2, *Plastics — Determination of Charpy impact properties — Part 2: Instrumented impact test*

ISO 291, *Plastics — Standard atmospheres for conditioning and testing*

ISO 306:2004, *Plastics — Thermoplastic materials — Determination of Vicat softening temperature (VST)*

ISO 527-2, *Plastics — Determination of tensile properties — Part 2: Test conditions for moulding and extrusion plastics*

ISO 1183 (all parts), *Plastics — Methods for determining the density of non-cellular plastics*

ISO 2039-1, *Plastics — Determination of hardness — Part 1: Ball indentation method*

ISO 2818, *Plastics — Preparation of test specimens by machining*

ISO 2580-1, *Plastics — Acrylonitrile-butadiene-styrene (ABS) moulding and extrusion materials — Part 1: Designation system and basis for specifications*

ISO 6402-1, *Plastics — Acrylonitrile-styrene-acrylate (ASA), acrylonitrile-(ethylene-propylene-diene)-styrene (AEPDS) and acrylonitrile-(chlorinated polyethylene)-styrene (ACS) moulding and extrusion materials — Part 1: Designation system and basis for specifications*

ISO 6603-1:2000, *Plastics — Determination of puncture impact behaviour of rigid plastics — Part 1: Non-instrumented impact testing*

ISO 11501, *Plastics — Film and sheeting — Determination of dimensional change on heating*

3 Material

Sheets shall be made of either ABS extrusion materials as defined in ISO 2580-1 or AEPDS (AES) or ASA extrusion materials as defined in ISO 6402-1, without fillers or reinforcing materials. The extrusion materials can contain additives such as processing aids, stabilizers, flame-protective agents and colorants. Compounds and additives of unknown identity shall not be used.

NOTE Legal conditions may necessitate a specific choice of extrusion material (see 4.3.3).

4 Requirements

4.1 Appearance

Sheets shall be substantially free from bubbles, voids, cracks, visible impurities and other defects which would make them unfit for the intended use. Surfaces shall be substantially smooth, if not embossed, and free from grooves, sink marks or damage. Colorants shall be homogeneously distributed throughout the material. Slight colour variations due to variations in the extrusion compound or processing conditions are admissible. The exact extent of variations in any of the above, as well as gloss level specifications, if required, shall be agreed between the interested parties. Sheets shall be examined in accordance with 5.3.

4.2 Dimensional tolerances

4.2.1 Thickness

Within any delivery of sheets, the maximum thickness variation from the nominal value, Δh_1 , in millimetres, shall satisfy the requirement.

$$|\Delta h_1| \leq (0,03 \text{ mm} + 0,04 \times h_n) \tag{1}$$

where h_n is the nominal sheet thickness, in millimetres.

Within any individual sheet, the maximum thickness variation, Δh_2 , in millimetres, shall satisfy the requirement.

$$|\Delta h_2| \leq (0,03 \text{ mm} + 0,02 \times h_n) \tag{2}$$

Testing shall be in accordance with 5.4.1.

4.2.2 Length and width

The nominal length, l_n , and nominal width, b_n , of sheets shall be as agreed between the interested parties. Unless agreed differently, the length shall be in the direction of extrusion.

For any individual sheet selected at random from any delivery, the tolerances on length and width shall be in accordance with Table 1. Testing shall be in accordance with 5.4.2.

Table 1 — Tolerances on length and width of sheets

Values in millimetres

Nominal dimension D_n	Tolerances	
	Length	Width
$D_n \leq 1\ 000$	+3 -1	+2 -1
$D_n > 1\ 000$	$+3 \times 10^{-3} \times l_n$ -1	$+2 \times 10^{-3} \times b_n$ -1

For rolled sheets, the minimum length shall be the nominal length.

4.2.3 Rectangularity

For any individual sheet selected at random from any delivery, the rectangularity tolerance, expressed as the difference in length of the diagonals, $|d_1 - d_2|$ (see Figure 1), shall satisfy the requirement

$$|d_1 - d_2| \leq 2 \times 10^{-3} \times \sqrt{(l_n^2 + b_n^2)} \quad (3)$$

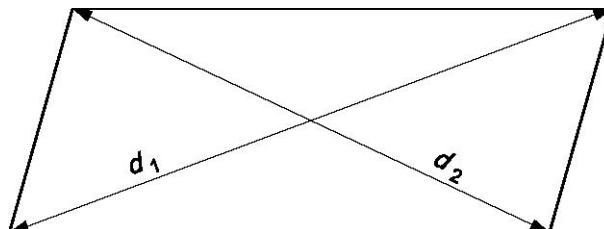


Figure 1 — Difference in length of diagonals, $|d_1 - d_2|$

Testing shall be in accordance with 5.4.3.

4.2.4 Bow of sheets in rolled form

For sheets in rolled form, a maximum bow of 20 mm in a 10 m length is permissible. Testing shall be in accordance with 5.4.4.

4.3 Properties

4.3.1 Mechanical and thermal properties

The basic mechanical and thermal properties shall be as specified in Tables 2 and 3. Guide values of other properties of extruded ABS, AEPDS (AES) and ASA sheets are given in Tables A.1 and A.2 in Annex A.

Table 2 — Mechanical and thermal properties — ABS

Property	Unit	Requirements (average values) for		Test method subclause	
		ABS-NI ^a	ABS-HI ^a		
Mechanical properties	Tensile stress at yield, σ_y	MPa	≥ 35	≥ 30	5.6.1
	Tensile modulus, E_t	MPa	$\geq 2\ 100$	$\geq 1\ 800$	5.6.2
	Charpy impact strength of unnotched specimens, a_{cu} , at $-20\ ^\circ\text{C}$ ^b	kJ/m ²	≥ 40	≥ 60	5.6.3
	Charpy impact strength of notched specimens, a_{cn} , at $-20\ ^\circ\text{C}$ ^b + $23\ ^\circ\text{C}$ ^b	kJ/m ²	≥ 10	≥ 15	5.6.4
	50 % impact-failure energy, E_{50} , at $h_n = 4\ \text{mm}$	J	≥ 30	≥ 55	5.6.5
	Ball indentation hardness, HB (test load 358 N)	N/mm ²	≥ 80	≥ 60	5.6.6
Thermal properties	Vicat softening temperature, VST (force 50 N, heating rate $50\ ^\circ\text{C}/\text{h}$)	$^\circ\text{C}$	90 to 105	85 to 105	5.7.1

^a NI: normal impact, HI: high impact.

^b Only valid for nominal sheet thicknesses $h_n \geq 4\ \text{mm}$ (see also 5.1.1).

Table 3 — Mechanical and thermal properties — AEPDS (AES) and ASA

Property	Unit	Requirements (average values) for		Test method subclause	
		AEPDS	ASA		
Mechanical properties	Tensile stress at yield, σ_y	MPa	≥ 30	≥ 30	5.6.1
	Tensile modulus, E_t	MPa	$\geq 1\,700$	$\geq 1\,500$	5.6.2
	Charpy impact strength of unnotched specimens, a_{cu} , at -20 °C ^a	kJ/m ²	≥ 60	≥ 80	5.6.3
	Charpy impact strength of notched specimens, a_{cn} , at -20 °C ^a + 23 °C ^a	kJ/m ²	≥ 25	≥ 30	5.6.4
	50 % impact-failure energy, E_{50} , at $h_n = 4\text{ mm}$	J	≥ 60	≥ 60	5.6.5
	Ball indentation hardness, HB (test load 358 N)	N/mm ²	≥ 70	≥ 60	5.6.6
Thermal properties	Vicat softening temperature, VST (force 50 N, heating rate 50 °C/h)	°C	85 to 105	85 to 105	5.7.1

^a Only valid for nominal sheet thicknesses $h_n \geq 4\text{ mm}$ (see also 5.1.1).

4.3.2 Behaviour on heating

The maximum shrinkage in the direction of extrusion shall not exceed the values given in Table 4 when measured using the method specified in 5.7.2 under the conditions given in Table 6. The test specimens shall be substantially free from bubbles and cracks after heating.

Tabelle 4 — Maximum shrinkage for thermoforming applications

Nominal thickness, h_n	0,25 mm	0,5 mm	1 mm	2 mm	4 mm	8 mm	> 8 mm
Max. shrinkage in the direction of extrusion	35 %	22 %	16 %	12 %	8 %	6 %	Not relevant

Intermediate values for other sheet thicknesses can be calculated by interpolation.

4.3.3 Physiological behaviour

Relevant legislation concerning physiological behaviour shall be taken into consideration.

5 Test methods

5.1 Test specimens

5.1.1 Preparation of test specimens

Representative test specimens shall be cut both longitudinally and transversely from locations evenly distributed over the length and width of the sheet. With sheets in rolled form, a 2 m sample shall be cut from the end of the roll to prepare test specimens. The surfaces of the test specimens shall be free from damage and faults in order to avoid notch effects. Should any burrs be formed on the test specimens during preparation, these shall be eliminated without damaging the surfaces of the specimens. If required, the cut edges shall be finished with abrasive paper (grain size 220 or finer), the direction of abrasion being along the length of the test specimens. If it is necessary to machine the sheet to reduce it to the thickness required, one original surface shall be left intact. In particular, test specimens over 4,2 mm thick intended to be used in the

tests described in 5.6.1 to 5.6.6 shall be machined down on one side to a thickness of $4,0 \text{ mm} \pm 0,2 \text{ mm}$ in accordance with ISO 2818.

5.1.2 Conditioning

Any production quality control test specimens shall be conditioned for at least 16 h in accordance with ISO 291 or as specified in the appropriate material standard. Shorter conditioning times may be used by agreement between the interested parties when it can be shown that there is no significant difference in the results obtained.

5.1.3 Test conditions

Testing shall be carried out under conditions which are in accordance with ISO 291, unless otherwise agreed between the interested parties or specified in the individual test standards.

5.2 Delivery condition

Surfaces and cut edges shall be visually examined for bubbles, voids, cracks, notches and swarf.

5.3 Appearance

Where possible, sheets shall be examined for visual defects by transmitted light using a suitable light source. Otherwise, sufficiently bright reflected light shall be used. Any defects thus identified shall be compared with the agreed specification (which may be either a written specification or in the form of reference samples) and the sheets classified accordingly.

5.4 Dimensions

5.4.1 Thickness, h

The thickness, h , shall be measured using suitable calibrated equipment meeting the requirements given in Table 5.

Table 5 — Error limits of equipment

Values in millimetres	
Nominal thickness, h_n	Error limit
$0,25 \leq h_n < 1,0$	$\leq +0,01$
$1,0 \leq h_n < 10,0$	$\leq +0,05$
$10,0 \leq h_n \leq 20,0$	$\leq +0,1$

5.4.2 Length, l , and width, b

The length, l , and width, b , shall be measured to the nearest 1 mm using suitable equipment. Measurements shall be made directly across the surface of the sheet and along the cut edge.

5.4.3 Rectangularity

For flat sheets, the rectangularity, expressed as the difference between the lengths of the diagonals, $|d_1 - d_2|$, as shown in Figure 1, shall be measured to the nearest 1 mm using a graduated ruler or tape measure.

5.4.4 Bow of sheets in rolled form

For sheets in rolled form, the bow shall be determined after the sheets have been pulled free from the rolls and measured against a straight edge. The bow shall be measured to the nearest 1 mm using suitable calibrated equipment.

5.5 Density

The density shall be determined in accordance with the appropriate part of ISO 1183.

5.6 Mechanical properties

5.6.1 Tensile stress at yield, σ_y

The tensile stress at yield, σ_y , shall be determined using at least five type 1B test specimens in each direction in accordance with ISO 527-2, using a test speed of 50 mm/min \pm 5 mm/min.

5.6.2 Modulus of elasticity in tension, E_t

The modulus of elasticity in tension, E_t , shall be determined using at least type 1B test specimens in each direction in accordance with ISO 527-2, using a test speed of 1 mm/min \pm 0,2 mm/min.

5.6.3 Charpy impact strength of unnotched specimens, a_{cu}

To determine the influence of surface effects caused by the processing conditions, the Charpy impact strength of unnotched specimens, a_{cu} , for nominal sheet thicknesses $h_n \geq 4$ mm shall be determined flatwise in accordance with ISO 179-1/1fU or ISO 179-2/1fU, using at least 10 test specimens cut in each direction. If the test specimens are machined down to the required thickness, the impact shall be applied to the machined surface.

5.6.4 Charpy impact strength of notched specimens, a_{cn}

To determine the influence of surface effects caused by the processing conditions, the Charpy impact strength of notched specimens, a_{cn} , shall be determined for nominal sheet thicknesses $h_n \geq 4$ mm, flatwise in accordance with ISO 179-1/1fA or ISO 179-2/1fA, using at least 10 double-notched test specimens cut in each direction. If the test specimens are machined down to the required thickness, the impact shall be applied to the machined surface.

5.6.5 Puncture impact behaviour

The puncture impact behaviour shall be determined as the 50 % impact-failure energy, E_{50} , in accordance with ISO 6603-1:2000, staircase method A.

5.6.6 Ball indentation hardness

The ball indentation hardness shall be determined in accordance with ISO 2039-1, using a test load of 358 N.

5.7 Thermal properties

5.7.1 Vicat softening temperature

The Vicat softening temperature shall be determined in accordance with method B50 of ISO 306:2004. The thickness of the test specimens shall be equal to the thickness of the sheet, except as follows:

- a) If the thickness exceeds 6,5 mm, the test specimens shall be reduced in thickness to between 3 mm and 6,5 mm by machining one surface (see ISO 2818), the other surface being left intact. The test surface shall be the intact one.
- b) If the thickness of the sheet is less than 3 mm, not more than three pieces shall be stacked together in direct contact to give a total thickness between 3 mm and 6,5 mm and the thickness of the upper (measured) piece shall be at least 1,5 mm. Stacking of pieces of lesser thickness does not always give the same test result.

5.7.2 Determination of shrinkage on heating

The shrinkage on heating shall be determined in accordance with the principles of ISO 11501. The principle of the test procedure is as follows:

- a) a tray containing a kaolin or talc bed is placed in a circulating-air oven and the temperature controlled such that the bed is within the specified temperature limits;
- b) the initial length between the reference marks on each test specimen is measured in the longitudinal direction;
- c) the test specimens are heated for a specified period of time at a specified temperature on the kaolin or talc bed in the circulating-air oven;
- d) the distance between the longitudinal reference marks is measured again after cooling, and the change in the length of each specimen calculated.

Cut at least three test specimens with dimensions of 100 mm × 100 mm from the centre and both sides of the sheet. The side test specimens shall be taken at least 50 mm from the edge of the sheet. Make one or more pairs of reference marks on the specimens in the extrusion direction. Measure the initial length, L_0 , between the pairs of marks with an accuracy of 0,1 mm at room temperature. Cover the test specimens with kaolin or talc and place them flat on the kaolin or talc bed in the circulating-air oven. The temperature and duration of the test shall be as given in Table 6.

Table 6 — Shrinkage test conditions for ABS, AEPDS (AES) or ASA sheet

Nominal sheet thickness, h_n mm	Test temperature °C	Duration of test ^a min
$0,25 \leq h_n < 1,0$	170 ± 2	10 ± 1
$1,0 \leq h_n < 4,0$	170 ± 2	20 ± 1
$4,0 \leq h_n < 8,0$	170 ± 2	30 ± 1
$8,0 \leq h_n$	170 ± 2	60 ± 1
^a The heating period until the test temperature is reached is not included.		

Remove the tray with the test specimens from the circulating-air oven. Allow to cool down to room temperature. Measure the length, L , of each specimen between the pairs of reference marks. Calculate the shrinkage, ΔL , for each pair of reference marks using Equation (4):

$$\Delta L = \frac{L_0 - L}{L_0} \times 100$$

Where

ΔL is the shrinkage on heating, in percent;

L_0 is the initial length in the direction of extrusion before heating, in millimetres;

L is the length in the direction of extrusion after heating, in millimetres.


Calculate the arithmetic mean of all the ΔL values for all the specimens.

If the test specimens show a tendency to curl or become wavy, this deformation can be limited by placing a 3 mm to 4 mm thick glass sheet over the test specimens at a distance of about 3 mm. The glass plate shall rest on spacers (e.g. made from cork) of equal height. Use weights, if necessary, to hold the glass plate in place. The weights and glass plate shall be heated to the appropriate temperature given in Table 6 before use.

If agreed between the interested parties, each specimen shall be examined after the test to ensure that no excessive cracks or bubbles have developed.


6 Designation

6.1 Example for ABS sheets

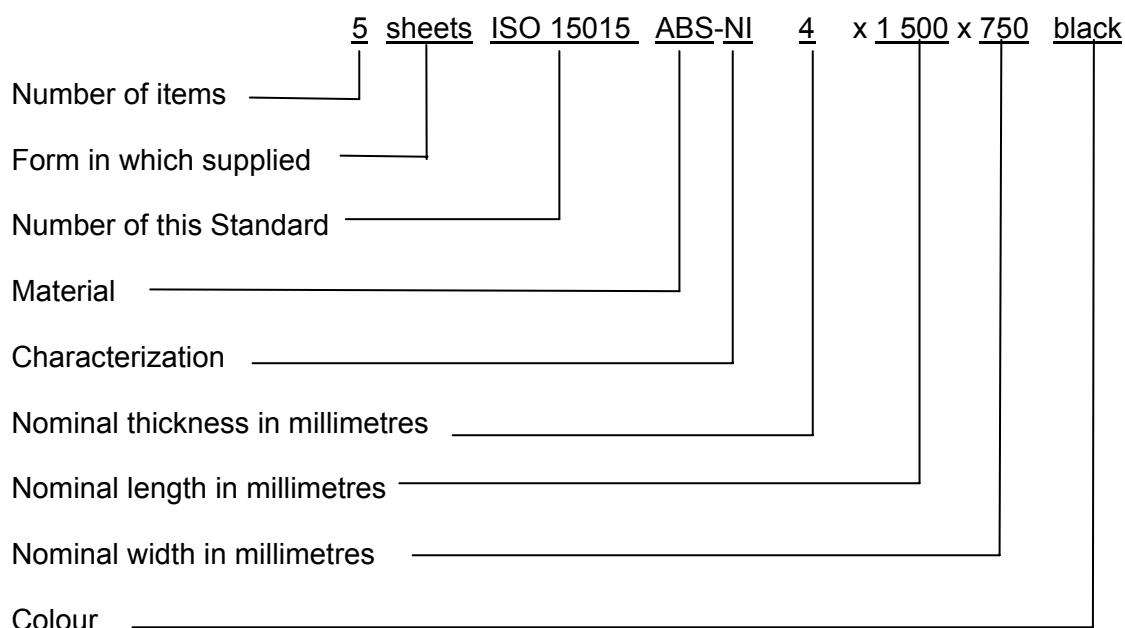

Designation: 5/sheets/ISO 15015/ABS-NI/4 x 1 500 x 750/black

6.2 Example for ASA sheets in rolled form

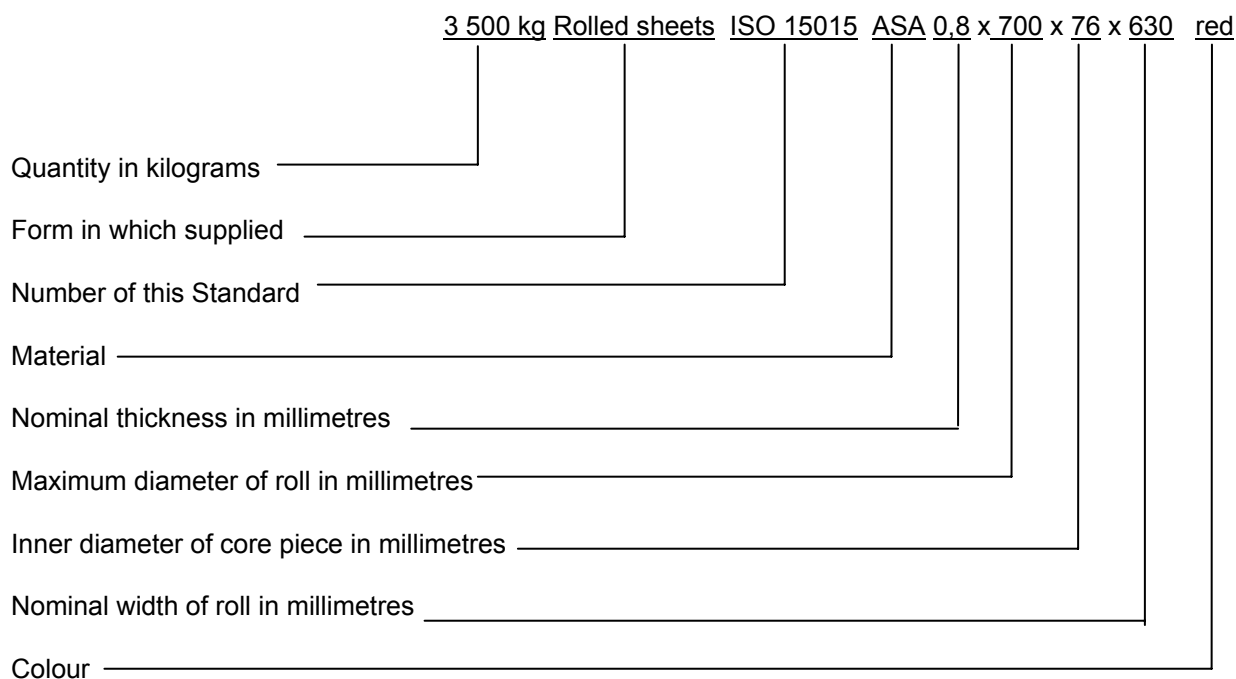

Designation: 3 500 kg/rolled sheets/iso 15015/ASA/0,8 x 700 x 76 x 630/red

7 Marking

Sheets and rolls that conform to this International Standard may be marked with the following information:

- a) the manufacturer's name, trade mark or identification mark;
- b) the reference number of this International Standard, ISO 15015;
- c) the designation of the material;
- d) the date of manufacture/batch number.

Annex A (informativ)

Additional guide values

Table A.1 — Guide values for further physical properties of ABS, AEPDS (AES) and ASA extrusion materials

Physical properties	Unit	Typical value	Test method
Density, ρ	g/cm ³	1,00 to 1,15	ISO 1183
Coefficient of thermal expansion, α (test range 23 °C to 80 °C)	K ⁻¹	approx. 1×10^{-4}	ISO 7991
Thermal conductivity, λ	W/m·K	approx. 0,17	ISO 8302:1991, method A
Surface resistivity, ρ_S	Ω	approx. 10^{13}	IEC 60093
Volume resistivity, ρ_D	$\Omega \cdot m$	approx. 10^{13}	IEC 60093
Water absorption, W_A , up to saturation at 23 °C	% by mass	approx. 1,7	ISO 62

Table A.2 — Guide values for further mechanical properties of ABS, AEPDS (AES) and ASA extrusion materials

Mechanical properties	Unit	ABS-NI ^a	ABS-HI ^a	AEPDS/ASA	Test method
Charpy impact strength of unnotched specimens, a_{cu} , at - 20 °C ^b	kJ/m ²	≥ 60	≥ 75	≥ 75	ISO 179-1/1eU or ISO 179-2/1eU
Charpy impact strength of notched specimens, a_{cn} , at -20 °C ^b + 23 °C ^b	kJ/m ²	≥ 10	≥ 15	≥ 20	ISO 179-1/1eA or ISO 179-2/1eA
Total penetration energy, E_{tot} , at $h_n = 4$ mm	J	≥ 35	≥ 60	≥ 45	ISO 6603-2
^a NI: normal impact, HI: high impact. ^b Only valid for nominal sheet thicknesses $h_n \geq 4$ mm (see also 5.1.1). Determined edgewise.					

Bibliography

- [1] ISO 62, *Plastics — Determination of water absorption*
- [2] ISO 6603-2, *Plastics — Determination of puncture impact behaviour of rigid plastics — Part 2: Instrumented impact testing*
- [3] ISO 7991, *Glass — Determination of coefficient of mean linear thermal expansion*
- [4] ISO 8302:1991, *Thermal insulation — Determination of steady-state thermal resistance and related properties — Guarded hot plate apparatus*
- [5] IEC 60093, *Methods of test for volume resistivity and surface resistivity of solid electrical insulating materials*